

Identifying vacancy complexes in compound semiconductors with positron annihilation spectroscopy: a case study of InN

Christian Rauch,^{1,*} Ilja Makkonen,² and Filip Tuomisto¹

¹*Department of Applied Physics, Aalto University,
P.O. Box 11100, FI-00076 Aalto, Espoo, Finland*

²*Helsinki Institute of Physics and Department of Applied Physics,
Aalto University, P.O. Box 14100, FI-00076 Aalto, Espoo, Finland*

(Dated: January 19, 2013)

We present a comprehensive study of vacancy and vacancy-impurity complexes in InN combining positron annihilation spectroscopy and ab-initio calculations. Positron densities and annihilation characteristics of common vacancy-type defects are calculated using density functional theory and the feasibility of their experimental detection and distinction with positron annihilation methods is discussed. The computational results are compared to positron lifetime and conventional as well as coincidence Doppler broadening measurements of several representative InN samples. The particular dominant vacancy-type positron traps are identified and their characteristic positron lifetimes, Doppler ratio curves and lineshape parameters determined. We find that V_{In} and their complexes with V_{N} or impurities act as efficient positron traps, inducing distinct changes in the annihilation parameters compared to the InN lattice. Neutral or positively charged V_{N} and pure V_{N} complexes on the other hand do not trap positrons. The predominantly introduced positron trap in irradiated InN is identified as the isolated V_{In} , while in as-grown InN layers V_{In} do not occur isolated but complexed with one or more V_{N} . The number of V_{N} per V_{In} in these complexes is found to increase from the near surface region towards the layer-substrate interface.

PACS numbers: 61.72.jd, 78.70.Bj, 71.60.+z, 61.72.Yx, 68.55.ln

Keywords: InN, vacancies, density functional theory, positron annihilation

I. INTRODUCTION

InN is a significantly cation-anion mismatched semiconductor compound¹ with many interesting properties and promising applications in opto-, and high-speed electronics². Intrinsic point defects have been accounted for multiple important mechanisms in the material³⁻⁷. Amongst them, In and N vacancies and their complexes are expected to be the dominant intrinsic acceptors and donors, respectively, according to latest density functional theory calculations⁸⁻¹². Nevertheless, unambiguous experimental evidence on their nature and characteristics is still relatively scarce. This is due to limitations stemming from intrinsic properties of InN, as well as challenges related to the growth of high-quality material. Strong surface electron accumulation in polar samples¹³ complicates the fabrication of Schottky contacts and therefore the application of standard electrical characterization methods such as deep level transient spectroscopy (DLTS) and capacitance voltage (C-V) profiling. Additionally, the high conductivities common for early as-grown InN layers together with the unavailability of bulk material strongly limit the use of electron paramagnetic resonance (EPR) based techniques. Positron annihilation spectroscopy is a powerful method for the investigation of vacancy type defects in semiconductors¹⁴ and largely not affected by the above mentioned challenges. Positrons can get trapped and annihilate at neutral and negatively charged open volume sites in the crystal lattice due to a locally reduced Coulomb repulsion. This increases the positron lifetime and nar-

rows the momentum distribution of annihilating electron-positron (e-p) pairs, both of which can be measured by recording the emitted annihilation γ radiation.

While direct experimental evidence on the behavior of N vacancies has been very limited, previous positron annihilation results show that In vacancy (V_{In}) related defects are incorporated in concentrations of $\sim 10^{16} - 10^{17} \text{cm}^{-3}$ during growth of both molecular beam epitaxy (MBE)¹⁵⁻¹⁷ and metal organic chemical vapor deposition (MOCVD)¹⁸ InN. Although V_{In} related defect concentrations are found to be low in the 10^{16}cm^{-3} range in thick layers of high quality as-grown material¹⁷ the experimentally observed concentrations are still by orders of magnitude higher than what could be expected based on first-principles calculations^{8,12}. A strong influence of the layer thickness on the vacancy concentrations has been found¹⁵, together with a commonly observed increase and qualitative change of the vacancy signal when approaching the layer-substrate interface^{7,15,18,19}. Growth parameters such as polarity⁷ and stoichiometry^{17,18} seem to have only minor impact. This suggests that the vacancy formation in InN is not dominated by thermal equilibrium processes but rather controlled by mechanisms such as local strain, the vicinity to other point and extended defects and/or limited surface diffusion during growth¹⁷. Nevertheless, no direct correlation between dislocation densities and vacancy formation has been found so far^{17,20}. In good agreement with the behavior of negatively charged defects below the branch point energy^{1,21}, n-type doping of InN by either Si^{19,22} or high energy particle irradiation⁶ leads to an increas-

ing incorporation of V_{In} related defects, while Mg-doped samples (with lowered Fermi level positions) show only low concentrations²³.

Unfortunately, the exact chemical identity of the vacancy defects detected in previous studies has remained largely unknown. Recent attempts however have shown that these limitations could in principle be overcome by careful modeling of positron annihilation parameters using ab-initio calculations^{23–25}. Despite this, a comprehensive theoretical study of positron annihilation in InN has still been missing.

In the following, we present an extensive identification of common vacancy and vacancy-impurity complexes in InN combining positron annihilation spectroscopy and ab-initio calculations. The employed computational and experimental methods are presented in section II. Calculated positron lifetimes and momentum distributions of annihilating e-p pairs are shown in section III for a variety of vacancies and vacancy complexes in InN. In section IV these are compared to experimental data from positron lifetime and Doppler broadening measurements, and the dominant vacancy defects in positron annihilation measurements of different as-grown, doped and irradiated InN samples are identified. A critical discussion of the results is presented in section IV D and possible implications are outlined.

II. METHODS

A. Experimental

Positron annihilation measurements are performed using a variable-energy (0.5–38 keV) slow positron beam. The Doppler broadening of the e-p annihilation radiation is recorded with two Ge-detectors with a combined Gaussian resolution function of 1.24 keV (0.66 a.u.) and 0.995 MeV (0.53 a.u.) full-width-at-half-maximum (FWHM) at 0.511 MeV in the conventional and coincidence Doppler setup^{26,27}, respectively. In the latter configuration, both annihilation photons are detected simultaneously and only counted if energy conservation is fulfilled ($E_{\text{tot}}=1.022\text{MeV}$). This significantly improves the peak-to-background ratio up to 10^6 and sharpens the detector resolution. To assure statistical reliability, spectra of $\sim 1 \times 10^6$ and 3×10^7 counts are accumulated for each measurement point in the conventional and coincidence setup, respectively.

In conventional Doppler mode the annihilation peak is analyzed using the common integrated lineshape parameters¹⁴ which represent the annihilation fractions in the low (S) and high (W) momentum parts of the spectrum. Integration windows of $|p_L(S)| < 0.4$ a.u. ($\Delta E_\gamma < 0.75$ keV) and 1.5 a.u. $< |p_L(W)| < 3.9$ a.u. (2.9 keV $< \Delta E_\gamma < 7.3$ keV) are chosen for the S and W parameter, respectively. In positron annihilation experiments the time-integrated annihilation parameter P_{exp} (e.g. average positron lifetime, annihilation lineshape,

S and W parameter) constitutes a weighted sum of the characteristic values of the present positron traps P_i and the crystal lattice P_b ,

$$P_{\text{exp}} = \eta_b P_b + \sum_{i=1}^n \eta_i P_i, \quad (1)$$

with η_b and η_i being the positron annihilation fractions of the lattice and the i -th defect, respectively.

The characteristic defect parameter P_i of a certain positron trap can hence be extrapolated from the recorded experimental signal P_{exp} , if bulk parameter and the positron annihilation fractions are known. The latter can be determined by decomposition of the positron lifetime spectrum into its n exponential decay components¹⁴, or by a complementary measurement of another time-integrated annihilation parameter whose set of characteristic parameters is well known. The bulk parameter is usually determined by measurement of a reference sample in which no trapping to vacancy defects can be observed (confirmed by positron lifetime measurements).

B. Computational

Our computational scheme²⁵ is based on the zero-positron-density limit of the two component density functional theory²⁸. Valence electron densities are calculated self-consistently using the local density approximation (LDA) and projector augmented-wave method (PAW)²⁹ implemented in the VASP code³⁰. All electronic structure calculations are performed using a 96-atom InN wurtzite supercell. Ionic positions are relaxed with a convergence criterium of 0.01 eV/Å for forces. Indium 4d electrons are treated as valence and an energy cut-off of 400 eV is chosen. The Brillouin zone is sampled with a 3^3 Monkhorst-Pack $\mathbf{k}$ -point mesh.

After deriving the electron densities in the lattice, the positron densities are solved independently in the calculated Coulomb potential due to electrons and nuclei and the e-p correlation potential. The calculation of the positron densities is performed in the so-called "conventional scheme", i.e. $n_+ \rightarrow 0$ is used and the e-p correlation potential is approximated in the zero positron density limit. This is only exact for the case of a completely delocalized positron in the crystal lattice (bulk) but is also justified for finite positron densities localized at a defect site when considering the positron and its screening cloud of electrons as a neutral quasi-particle which does not affect the surrounding average electron density. The LDA²⁸ in the state-dependent scheme²⁷ is used for the description of many-body effects in the calculation of positron annihilation rates and the momentum distributions of annihilating e-p pairs. In this approximation, the momentum density $\rho(\mathbf{p})$ of annihilating e-p pairs is expressed as

$$\rho(\mathbf{p}) = \pi r_e^2 c \sum_j \gamma_j \left| \int d\mathbf{r} e^{-i\mathbf{p} \cdot \mathbf{r}} \psi_+(\mathbf{r}) \psi_j(\mathbf{r}) \right|^2, \quad (2)$$

where r_e is the classical electron radius, c the speed of light and $\psi_+(\mathbf{r})$, $\psi_j(\mathbf{r})$ the positron and electron wavefunctions, respectively. The summation is performed over all occupied electron states and γ_j is the position independent electron-state-dependent enhancement factor²⁷ which takes into account the increase in annihilations due to the screening electron density around the positron.

In order to be able to compare the calculated 3D momentum density to 1D experimental spectra we integrate the calculated spectra over the wurtzite m -plane. To account for the experimental detector resolution the calculated momentum distributions are additionally convoluted with a Gaussian resolution function of 0.53 a.u. and 0.66 a.u. FWHM for the comparison with coincidence and conventional Doppler spectra, respectively. The line shape parameters S and W are calculated from the spectra convoluted with 0.66 a.u. FWHM using the above momentum windows. The positron lifetime τ is determined as the inverse of the annihilation rate λ , which is given as

$$\lambda = \frac{1}{\tau} = \pi r_e^2 c \int d\mathbf{r} n_+(\mathbf{r}) n_-(\mathbf{r}) \gamma(n_-(\mathbf{r})), \quad (3)$$

with $\gamma(n_-(\mathbf{r}))$ the enhancement factor²⁷ in the LDA.

In our calculations we made two further simplifications, i.e. all defects are considered in the neutral charge state and forces due to localized positrons are neglected. Adding negative (positive) charge is expected to lead to an additional inwards (outwards) relaxation¹¹, while the Coulomb force of localized positrons is directed outwards²⁵. The exact charge state of defect complexes is often unknown in experiments, hence is not safe to be assumed without further prove. On the other hand, only considering the positron-induced forces³¹ leads to an overestimation of the outwards relaxation. Nevertheless, careful testing showed that the effects of additional charge and localized positrons on the annihilation characteristics can be neglected compared to changes between different defects. Also, trends in the calculated spectra are valid irrespective of which approximation is used.

III. COMPUTATIONAL RESULTS

The optimized lattice constants for wurtzite InN are calculated as $a = 3.510$ Å, $c = 1.610$ Å and $u = 0.379$, in good agreement with literature^{11,32}. The positron density in the InN lattice is fully delocalized (see Fig. 1(a)), and a positron lifetime of 157 ps is determined. The difference to the experimental lifetime value¹⁵ of ~ 180 ps stems from using the LDA enhancement factor. The choice of the LDA is motivated by our focus on the calculation of momentum distributions²⁵. In this approximation, good agreement with experiments is achieved²⁵ for positron lifetime differences, $\Delta\tau = \tau_{\text{defect}} - \tau_{\text{bulk}}$, rather than absolute values. When analyzing computational positron lifetimes, it should be noted that calcu-

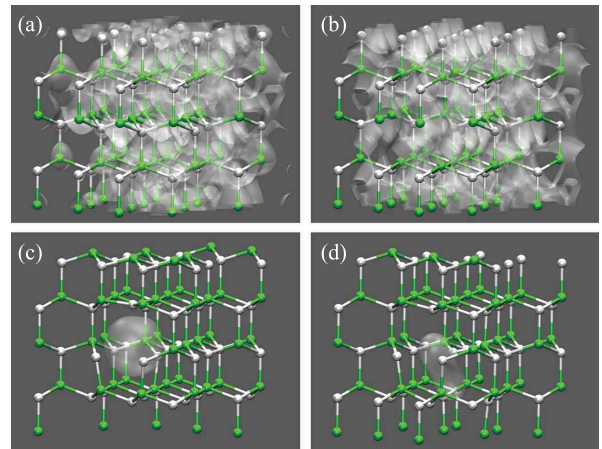


FIG. 1: (Color online) Iso-surface plot of the calculated positron density (transparent sphere) in the relaxed lattice structure of the (a) InN lattice and (b) $4V_N$, (c) V_{In} , and (d) $2V_{In}$ defects. Light grey (silver) and dark grey (green) balls indicate N and In ions, respectively.

lated values are sensitive to the size of the relaxed open volume (i.e. overlap of positron and electron density), and small differences in relaxation of a few percent can lead to lifetime differences of a few ps.

The modeled momentum distribution of annihilating e-p pairs in the InN lattice is displayed in Fig. 2. The annihilation spectrum is symmetrical and is hence folded at its center at 0 a.u (511 keV). In the low momentum part of the spectrum annihilations with In $5p$ and N $2p$ valence electrons dominate while contributions from tighter bound core electrons (In $4d$ and N $2s$) become more important in the higher momentum part of the spectrum.

A. Isolated In vacancy

The relaxed defect geometry of the V_{In} is shown in Fig. 1(c) together with the calculated positron density in the lattice. An outwards relaxation of the neighboring N ions from their initial positions is observed in good agreement with Duan *et al.*¹¹. The positron density shows a strong localization at the defect site which means that V_{In} act as efficient positron traps in InN. The calculated positron lifetime difference to the InN lattice is 85 ps, which is in good agreement with the ~ 80 ps observed in experiments^{15,19}. Results obtained with the atomic superposition (ATSUP) method³³ show for positrons trapped at the V_{In} increased annihilations with loosely bound valence electrons (In $5p$ and N $2p$) while annihilations with tighter bound core electrons (most importantly In $4d$) decrease significantly. This leads to an overall narrowing of the annihilation peak compared to the InN lattice (see Fig. 2).

For a more detailed analysis of the momentum spectrum we examine its so-called ratio curve in Fig. 3(a), in which the calculated momentum distribution is displayed divided by the spectrum for the defect-free InN lattice to

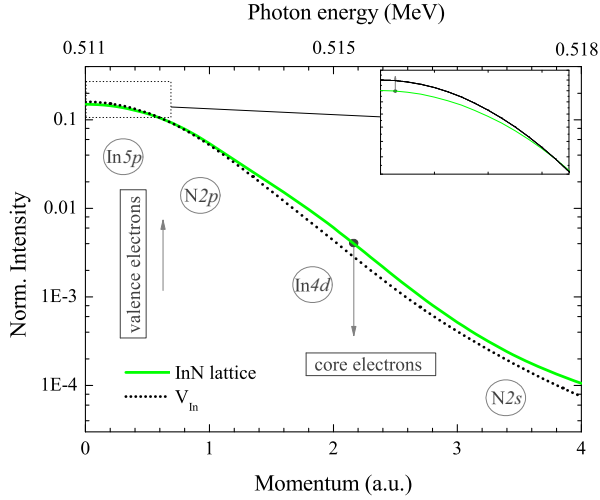


FIG. 2: (Color online) Calculated momentum density of annihilating e-p pairs in the delocalized state of the InN lattice and trapped at the V_{In} , respectively. Trends in the spectra are indicated with respect to the InN lattice.

accentuate the defect-induced changes. The ratio curve for the V_{In} exhibits a distinct line shape with a maximum of roughly 1.08 at the peak center region (0 a.u.). For momenta above 0.6 a.u. the spectrum drops below 1 and an articulate shoulder is visible at 1.2 a.u. which has been determined by ATSUP calculations to stem from annihilations with N $2p$ electrons. At around 3.3 a.u. a second broad peak appears with an intensity of around 0.8 relative to the InN lattice.

The characteristic relative line shape parameters (for the conventional detector resolution of 0.66 a.u.) of the V_{In} momentum distribution spectrum are calculated as 1.057 and 0.78 for S and W, respectively. Fig. 4 shows the calculated values plotted in a SW-plot.

B. In vacancy complexes

Recent DFT results¹¹ suggest that V_{In} would form complexes with each other and predict a significant decrease in formation energies when going from a single V_{In} to $2V_{\text{In}}$ and $3V_{\text{In}}$ complexes. Motivated by these results we calculate the momentum densities and positron lifetimes of the $2V_{\text{In}}$ and $3V_{\text{In}}$ in their most favorable configurations¹¹. In the $2V_{\text{In}}$ pair the two vacancies are located out-of-plane (with respect to the c-plane) on next-nearest neighbor positions, and for the $3V_{\text{In}}$ complex an additional vacancy is added in the c-plane sharing the same N atom. As expected, both $2V_{\text{In}}$ and $3V_{\text{In}}$ complexes show localized positron densities. Although the V_{In} are only situated on next-nearest neighbor sites their open volumes are connected, showing e.g. a handlebar-like structure for the positron density at the $2V_{\text{In}}$ pair (see Fig. 1(d)).

Positron annihilation characteristics of the $2V_{\text{In}}$ defect are very similar to the isolated V_{In} . The calculated

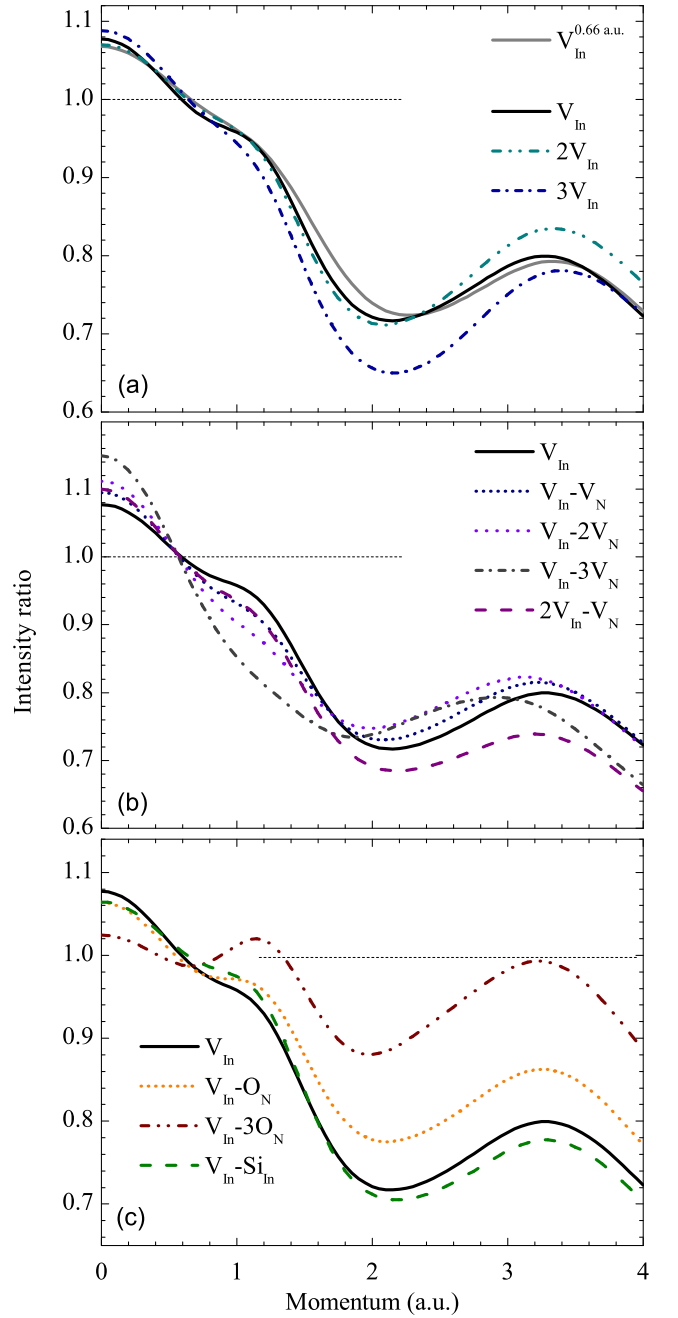


FIG. 3: (Color online) Ratio curves of the calculated momentum densities of annihilating e-p pairs in selected vacancy complexes in InN. All spectra are convoluted with a Gaussian of 0.53 a.u. FWHM (except $V_{\text{In}}^{0.66 \text{ a.u.}}$, FWHM = 0.66 a.u.) and divided by the momentum density spectrum of the InN lattice.

positron lifetime is equal and the lineshape parameters are very close to the isolated case, with $\Delta\tau = 85$ ps, $S = 1.055$ and $W = 0.77$ (see Fig. 4). In the ratio curve in Fig. 3(a), a slight increase of the peak at 3.3 a.u. is visible but the absolute intensity at these momentum values is already reduced by $\sim 10^3$ compared to the peak maximum (see Fig. 2) and discrimination (in experiments) is hence considerably complicated.

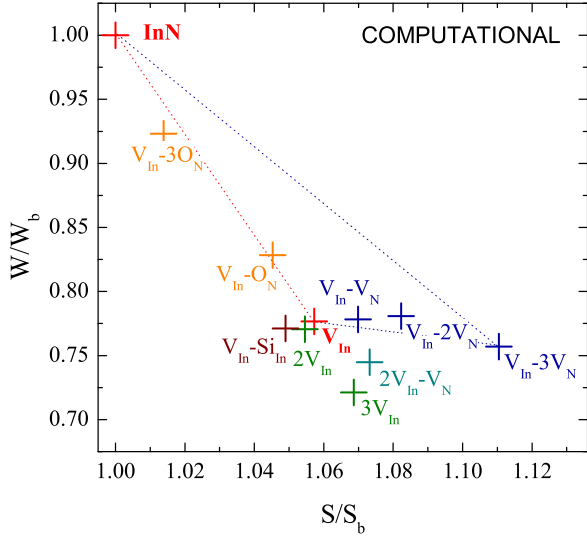


FIG. 4: (Color online) SW-plot of conventional lineshape parameters S and W for the calculated momentum distributions of annihilating e-p pairs trapped at different vacancy type defects in InN.

For the $3V_{\text{In}}$ complex we calculate an increase in the positron lifetime of roughly 10 ps compared to the isolated V_{In} ($\Delta\tau = 94$ ps). Additionally, the ratio curve changes significantly with an increased peak maximum and a more pronounced drop at 2.1 a.u. This is also visible in the change of the lineshape parameters to $S = 1.069$ and $W = 0.72$. Nevertheless, further analysis shows that the relative lineshape of the $3V_{\text{In}}$ and V_{In} are very similar and the spectrum of the V_{In} can nearly be reproduced from the $3V_{\text{In}}$ spectrum by assuming a positron annihilation fraction of $\eta \approx 0.8$ (see Eq. 1). This is also visible in the SW-plot (Fig. 4) in which the characteristic point of the $3V_{\text{In}}$ falls on an extension of the line connecting the InN lattice point and the V_{In} . For measurement points lying between the V_{In} and the InN lattice, the $3V_{\text{In}}$ and V_{In} can therefore only be distinguished with precise knowledge of the positron annihilation fraction. This is in practice limited by the achievable accuracy in the separation of lifetime components in positron lifetime measurements.

C. N vacancy complexes

For most of the Fermi level regions, V_{N} in InN are supposed to be donors in the 3+ charge state⁸ (hence repelling positrons) and possess a substantially smaller open volume compared to the V_{In} , due to the large size difference between In and N atoms. Both suggests strongly that isolated V_{N} can not act as positron traps in InN. Nevertheless, this may not count for larger complexes of several V_{N} which possess a positive binding energy (compared to isolated V_{N}) according to recent first-principles calculations⁹. The increased open volume in

these defects could in principle promote a localization of the positron density. Additionally, the V_{N} complexes are assumed to adapt negative charge states for elevated Fermi level positions which additionally supports trapping.

To assess whether V_{N} or its complexes could act as positron traps in InN, we calculated the electron and positron densities for the isolated V_{N} and V_{N} complexes of up to 4 N vacancies in the neutral charge state. The defect structure and positron density for the $4V_{\text{N}}$ complex are shown in Fig. 1(b), exemplarily. We find that the positron density for all calculated V_{N} complexes is clearly delocalized and no bound positron state exists at V_{N} or V_{N} complexes. Hence, isolated V_{N} and pure V_{N} clusters (in the neutral charge state) cannot be detected using positron annihilation spectroscopy. For the case of negatively charged V_{N} complexes the formation of weakly localized hydrogenic positron states around the defects is expected which possess very similar annihilation characteristics to the defect free lattice but might be detectable through their specific temperature behavior¹⁴.

D. Mixed In and N vacancy complexes

Apart from pure V_{In} and V_{N} complexes, a positive binding energy is predicted between isolated V_{In} and V_{N} , which should promote the formation of divacancies ($V_{\text{In}}-V_{\text{N}}$) and larger mixed vacancy complexes in the material¹¹. We calculate the positron densities and positron annihilation characteristics for the relaxed lattice structures of a variety of mixed vacancy complexes in InN, namely $V_{\text{In}}-V_{\text{N}}$, $V_{\text{In}}-2V_{\text{N}}$, $2V_{\text{In}}-V_{\text{N}}$ and $V_{\text{In}}-3V_{\text{N}}$. As expected, the increased open volume leads in all structures to a clear localization of the positron density at the defect site. The calculated positron lifetimes are close to the V_{In} lifetime for the $V_{\text{In}}-V_{\text{N}}$ and $V_{\text{In}}-2V_{\text{N}}$, with $\Delta\tau = 86$ and 88 ps, but increase to 99 and 109 ps for the $V_{\text{In}}-3V_{\text{N}}$ and $2V_{\text{In}}-V_{\text{N}}$, respectively. Fig. 3(b) shows the ratio curves of the computed momentum distributions. A systematic trend compared to the isolated V_{In} is visible in the spectra when adding an increasing amount of V_{N} around a single V_{In} . A strong increase of the zero momentum maximum to over 1.15 for the $V_{\text{In}}-3V_{\text{N}}$ is visible which is related to the increase in open volume. At the same time, the intensity of the shoulder at 1.2 a.u. decreases with increasing number of V_{N} until it entirely disappears for the $V_{\text{In}}-3V_{\text{N}}$. The ratio curve of the $2V_{\text{In}}-V_{\text{N}}$ is close to the $V_{\text{In}}-V_{\text{N}}$ for lower momentum values but starts to deviate at around 1.4 a.u. with lower intensities at higher momenta, due to reduced annihilation with In 4d electrons.

The characteristic line shape parameters of the calculated complexes develop accordingly and show a clear deviation from the InN - V_{In} line in Fig. 4, which is already visible for the divacancy and intensifies with increasing number of V_{N} . S and W values for the $V_{\text{In}}-V_{\text{N}}$, $2V_{\text{In}}-V_{\text{N}}$, $V_{\text{In}}-2V_{\text{N}}$ and $V_{\text{In}}-3V_{\text{N}}$ are determined as 1.070 and 0.78, 1.082 and 0.78, 1.073 and 0.75, and 1.115 and 0.76, respectively.

E. Vacancy-impurity complexes

III-vacancy donor-impurity complexes are well established in III-Nitrides. In GaN, a binding energy of 1.6 eV has been determined³⁴ between O_N and V_{Ga} . The binding energy between V_{Ga} and Si_{Ga} is considerably smaller (V_{Ga} and Si_{Ga} are only next-nearest neighbours) but still positive³⁵. Recent ab-initio calculations¹⁰ predict also in InN a reduction of the defect formation energy for $V_{In}-O_N$ complexes compared to the isolated case, and even stronger for the case of $V_{In}-3O_N$.

Hence, we take a look at the relaxed defect structures and positron densities for the $V_{In}-O_N$, $V_{In}-3O_N$ and $V_{In}-Si_{In}$. For all complexes the positron density is localized at the defect site. The calculated positron lifetimes to the InN lattice are again very close to the isolated V_{In} case with 85, 86 and 88 ps for the $V_{In}-Si_{In}$, $V_{In}-O_N$ and the $V_{In}-3O_N$, respectively. In the ratio curves of the momentum densities shown in Fig. 3(c) the peak maximum decreases with increasing number of O ions, while the intensity in the spectral range above 0.9 a.u. increases including the shoulder at 1.2 a.u. and the peak at 3.4 a.u. The form of the $V_{In}-O_N$ ratio curve resembles the case of V_{In} trapping with a reduced annihilation fraction of $\eta \approx 0.8$. This can also be seen in the SW-plot (Fig. 4) where the characteristic points for all calculated vacancy impurity complexes roughly fall on the InN - V_{In} line, meaning that their lineshape parameters could be reproduced from the V_{In} values assuming incomplete annihilation fractions. The spectrum of the $V_{In}-Si_{In}$ is very close to the V_{In} and hence hardly distinguishable in experiments. The case is different for the ratio curve of the $V_{In}-3O_N$ which possesses distinct features with the shoulders at 1.2 and 3.6 a.u., respectively, which should be measurable in coincidence Doppler measurements. The corresponding lineshape S (W) parameters of the calculated vacancy-impurity complexes are 1.045 (0.83), 1.014 (0.92) and 1.049 (0.77) for the $V_{In}-O_N$, $V_{In}-3O_N$ and $V_{In}-Si_{In}$, respectively.

F. Summary and discussion

Our calculations can be summarized with following conclusions. Isolated V_N and pure V_N complexes in the neutral or positive charge state do not localize the positron density and hence cannot be detected with positron annihilation spectroscopy. When negatively charged, they might act as shallow traps¹⁴ for positrons. Isolated V_{In} are efficient positron traps in InN with annihilation characteristics (positron lifetime, ratio curve, lineshape parameters) which are clearly distinguishable from the InN lattice values. This is the case for all calculated defect complexes which include at least one V_{In} . Apart from the $2V_{In}-V_N$ and $V_{In}-3V_N$ complexes, their calculated positron lifetime values are very similar with lifetime differences from 85 ps to 95 ps compared to the InN lattice value. Due to the experimental accuracy their distinction based on characteristic defect lifetimes is in

practice not feasible. The case is different for $2V_{In}-V_N$ and $V_{In}-3V_N$ complexes, where lifetimes are higher with 109 and 99 ps difference to the InN lattice, respectively. Distinction between the isolated V_{In} and the calculated complexes can be achieved when considering their momentum distributions. For the characteristic lineshape parameters of mixed $V_{In}-nV_N$ complexes a clear deviation from the InN - V_{In} line is found in Fig. 4, with a strong increase of the S parameter with nearly constant W parameter for an increasing number of V_N around the V_{In} . Its origin is revealed in the corresponding ratio curves as a growing peak maximum and nearly constant area for momenta between 1.5 and 3 a.u., where the dominant contributions to the S respectively W parameter stem from. The most distinct feature of these $V_{In}-nV_N$ complexes is identified in the disappearing shoulder at 1.2 a.u.

The characteristic points of the calculated vacancy-impurity and pure V_{In} complexes do not show such deviation but fall on (an extension of) the InN - V_{In} line. Accurate determination of the annihilation fractions would be necessary for an unambiguous identification of the $3V_{In}$ complex. The $V_{In}-3O_N$ complex exhibits some unique features in its ratio curve, but $V_{In}-Si_{In}$ and $2V_{In}$ are hardly distinguishable from the isolated V_{In} .

IV. EXPERIMENTAL SPECTRA AND DEFECT IDENTIFICATION

In order to identify the dominant positron traps in common InN material we investigate a variety of as-grown and irradiated layers that were grown by different growth methods. An overview of a representative selection of measured samples is given in Table I. Sample I is MBE-grown material⁶ which has been irradiated with 2 MeV He ions to a fluence of $8.9 \times 10^{15} \text{cm}^{-2}$, sample II and III are as-grown Si-doped³⁶ and undoped³⁷ InN layers deposited by MBE and MOCVD, respectively. Details on the growth and characteristics of the samples can be found elsewhere^{6,7,18,19,36,37}. Sample I and II show a strong change in the Doppler broadening signal when approaching the interface, which is a common feature in several previously investigated InN samples^{7,15,18,19}.

TABLE I: Studied samples and experimentally determined lineshape parameters of the respective dominant positron trap. All parameters are extrapolated to saturation trapping and divided by the reference values measured in InN lattice.

ID	Sample	Layer:		Interface:	
		S/S _{ref}	W/W _{ref}	S/S _{ref}	W/W _{ref}
I	MBE, irr.	1.042	0.80	1.083	0.78
II	MBE, Si-doped	1.051	0.83	1.077	0.81
III	MOCVD	1.052	0.81	/	/

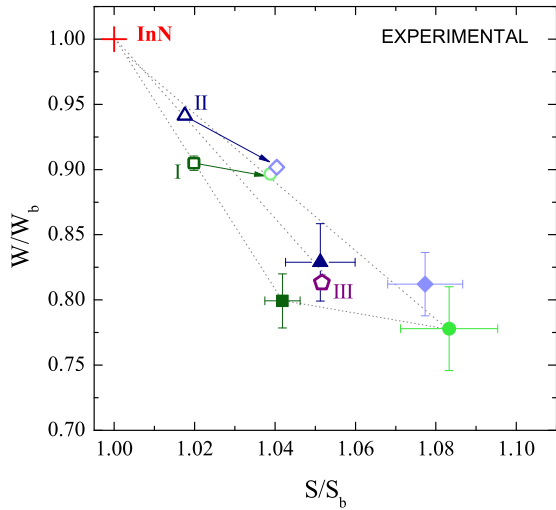


FIG. 5: (Color online) Experimentally determined S and W values from conventional Doppler broadening setup for different samples (see Table I). Open symbols correspond to directly measured values, closed symbols have been extrapolated using trapping fractions estimated from positron lifetime measurements. Light colors are used for points at high implantation energies, close to the interface (see arrow), while dark colors indicate points for low implantation energies, in the InN layer region.

Therefore, the interface region is investigated separately in these two samples (see section IV C).

Conventional Doppler broadening (Fig. 5) as well as coincidence Doppler (Fig. 6) spectra are recorded for all samples. The recorded momentum distributions for samples I and II are extrapolated to saturation trapping, using annihilation fractions determined from previously recorded positron lifetime measurements. An extensive description of the positron lifetime data is published elsewhere^{7,19}. All experimental momentum distributions are shown as ratio curves divided by the spectrum of a suitable reference for the InN lattice. The reference sample has been carefully analyzed using positron lifetime spectroscopy and no positron annihilation in trapped states at vacancy defects is observed³⁸. All samples are measured perpendicular to the c -axis.

A. Irradiation-induced defects

Positron lifetime measurements⁷ of the layer region of sample I show one dominant positron trap with a characteristic lifetime of 260 ps, and an annihilation fraction of $\eta = 0.47$ is determined for the trap. The recorded line-shape parameters from conventional Doppler broadening measurements are extrapolated accordingly and displayed in Fig. 5. Characteristic line shape parameters of $S = 1.042$ and $W = 0.80$ are evaluated for the dominant defect in this region.

The extrapolated ratio curve of sample I is shown in Fig. 6(a). When comparing the experimentally determined defect ratio curve to the calculated momentum dis-

tributions in section II B we find good agreement with the spectrum of the isolated V_{In} for the most of the spectral range. In the central region of the peak slightly higher intensities are found in the calculated spectrum compared to the experimental one. This region is mostly sensitive to the size of the open volume of the positron trap, with higher intensities for larger volumes. The calculated $2V_{\text{In}}$ and $V_{\text{In}}\text{-O}_N$ complexes possess an overall rather similar shape of the ratio curve and based on this also have to be considered as possible sources of the defect signal. Nevertheless, the available lifetime data does not support the reduced annihilation fraction which would be required for an identification of the experimental spectrum with the $V_{\text{In}}\text{-O}_N$. Although the differences between the V_{In} and $2V_{\text{In}}$ complex are more subtle and hence the $2V_{\text{In}}$ cannot be ruled out contributing to the signal, the ratio curve of the V_{In} gives the best overall approximation of the experimental spectrum. Therefore we identify the positron trap created in irradiated InN with the isolated V_{In} .

B. Defects in as-grown samples

The experimentally determined S and W parameters from conventional Doppler broadening for the as-grown samples II and III are displayed in Fig. 5. Positron lifetime measurements¹⁹ show a annihilation fraction of $\eta = 0.34$ in the dominant positron trap for sample II. Based on this, the characteristic lineshape parameters for this defect are estimated as 1.051 and 0.83 for S and W , respectively. This is close to the as-measured line shape parameters of sample III, i.e. $S = 1.052$ and $W = 0.81$. For this sample no lifetime data is available. In Fig. 6(b) the respective ratio curves recorded with coincidence Doppler measurements are displayed. The extrapolated ratio curve of both sample II and the as-measured spectrum of sample III show a very similar line shape. The bigger scatter in the former is due to a smaller annihilation fraction.

Compared to sample I, the as-grown samples II and III show several differences in their ratio curves. First, the intensity in the peak center region is clearly increased. The intensity difference to the InN lattice is thereby magnified by about 35 % compared to the spectrum of sample I. This is supported by very accurate statistics in this spectral region. Second, a significant decrease of the shoulder at 1.2 a.u. is visible, also with high statistical accuracy. Third, the drop at 2 a.u. is less pronounced, followed by slightly higher intensities in the high momentum region of the spectrum. Nevertheless, stronger scatter starts to dominate this region.

A comparison with the calculated defect spectra in section III reveals that these changes coincide with the effects of the decoration of a V_{In} by V_N , as presented in Fig. 3(b). Especially the characteristic decrease of the shoulder at 1.2 a.u. in ratio curves of the experimental spectra cannot be correlated with any other calculated vacancy defect complex (see additionally Hautakangas

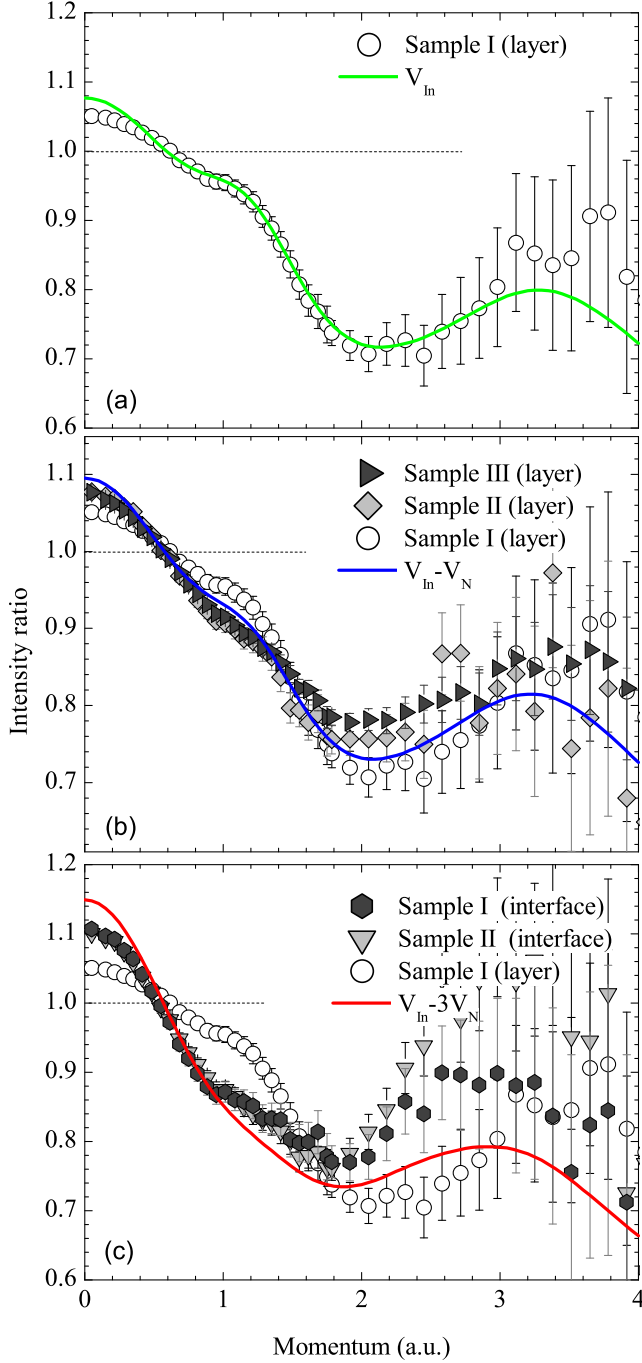


FIG. 6: (Color online) Experimental coincidence Doppler spectra of the investigated samples in the layer (a,b) and interface (c) region. The data has been divided by a suitable reference spectrum for the InN lattice. Computational ratio curves are shown for comparison.

*et al.*²⁴). This is also expressed in the observed deviation of the characteristic lineshape parameters of sample II and III from the line determined by the characteristic points of sample I and the InN lattice in Fig. 5. A similar trend can be observed for the calculated $V_{\text{In}}-nV_{\text{N}}$ parameters in Fig. 4. Judging from the amount of the ob-

served changes in the ratio plots an identification of the experimental spectra with $V_{\text{In}}-V_{\text{N}}$ is most feasible, with possible influence from the $V_{\text{In}}-2V_{\text{N}}$. This assignment is in good agreement with the positron lifetime data¹⁹.

C. Defects at the Interface

A strong change in the Doppler broadening signal is observed for sample I and II close to the interface region, as visible in Fig. 5. From positron lifetime data in this region^{7,19} we determine a positron annihilation fraction of $\eta = 0.47$ and $\eta = 0.52$ at the dominant positron traps in samples I and II, respectively. The characteristic defect lifetime at the interface is slightly increased compared to the layer region. The extrapolated line shape parameters are determined as 1.083 (0.78) and 1.077 (0.81) for S (W) in samples I and II, respectively, and show an even stronger deviation from the line defined by the characteristic points of sample I and the InN reference as already observed in section IV B. The characteristic SW points of both interfaces coincide within the statistical accuracy. This indicates that the same dominant positron trap is present in both samples, which is also shown in the extrapolated ratio curves shown in Fig. 6(c). In both samples a strong increase in the peak center intensity to about 1.12 is visible, which is over 2-fold compared to that observed in the irradiated layer. Additionally, the signal drops straight to the minimum at 2 a.u. without showing anymore the shoulder which is visible in the layer region of both samples. The observed trends are qualitatively very similar to the ones described in the previous section for the layer region of samples II and III, but intensified. Therefore, we identify the induced changes with an increase in the decoration of V_{In} with V_{N} . When comparing to the calculated momentum distributions in section III, best agreement is found for the spectrum of the $V_{\text{In}}-3V_{\text{N}}$ complex. Results from both conventional Doppler broadening (Fig. 5) and positron lifetime spectroscopy additionally support this assignment^{19,38}.

D. Summary and discussion

Based on the above presented data we are able to identify the dominant positron trap created in high-energy particle irradiation of MBE grown InN layers as the isolated V_{In} , while in as-grown MBE and MOCVD material the observed defect is a mixed $V_{\text{In}}-V_{\text{N}}$ vacancy complex. The changes at the interface in both irradiated material and as-grown layers are assigned to the formation of larger $V_{\text{In}}-nV_{\text{N}}$ complexes with an average of about 3 V_{N} surrounding the V_{In} . It has to be noted that the positron implantation profile for the chosen interface point (12 keV) is already considerably broadened and hence signal from a wide area of the layer is averaged. The observed complexing of V_{In} and V_{N} is in good agreement³⁹ with existing data on the electron mobility in

these samples³ and might be the reason behind observed superior transport properties.

The measured Doppler broadening of the annihilation γ radiation is caused by the momentum component of annihilating e-p pairs along the detection direction¹⁴. All our experimental spectra are recorded perpendicular to the c -axis but the exact detection direction in the c -plane is not identified. We compare the experimental spectra to computational momentum distributions integrated over the m -plane. The induced uncertainty could in principle cause difficulties for the exact defect identification, as small differences between the different lattice directions are present³¹. Nevertheless, these are minor compared to differences between the calculated spectra of different defect complexes and hence pose no problem in our case. This counts especially when interpreting changes in the momentum distributions rather than absolute values.

Our data accentuates the advantage of high-quality coincidence Doppler²⁶ spectra for the identification of defect identities. Apart from the advanced experimental resolution compared to conventional Doppler measurements which helps to distinguish defect-induced changes (see Fig. 3(a)), important features in the spectra might be lost when only regarding the integrated lineshape parameters S and W . This is the case, e.g., for the observed disappearance of the shoulder at 1.2 a.u. which is identified as an unique feature of the $V_{\text{In}}-nV_{\text{N}}$ complexes. The commonly used integration windows for the S and W parameters cannot include this momentum area, in order to avoid correlation effects¹⁴. Irrespective of this, a shift of the lower limit of the W -parameter window to 2.2 a.u. (for a detector resolution of 1.24 keV) would be beneficial in future positron experiments in InN in order to maximize the visibility of defect-induced changes (see Fig. 3).

V. CONCLUSION

We present the identification of dominant vacancy-type positron traps in different representative InN samples by combining positron lifetime and Doppler broadening spectroscopy with ab-initio calculations of the positron annihilation characteristics. Calculated momentum distributions of annihilating electron positron (e-p) pairs in different vacancy type defects are compared to high resolution measurements of the Doppler broadened e-p annihilation radiation acquired with the coincidence Doppler technique. We find that isolated V_{N} or pure V_{N} complexes do not trap positrons. During high-energy particle irradiation isolated V_{In} are created, which are the dominant positron trap in such samples at room temperature. In as-grown InN samples on the other hand, V_{In} do not occur isolated but complexed with one or more V_{N} . The observed changes of the Doppler broadening signal close to the interface are identified with an increasing amount of V_{N} surrounding the V_{In} . The characteristic lifetimes, ratio curves and S and W parameters for the identified defects are determined.

Acknowledgments

The authors thank the groups of W. Schaff at Cornell University, J. Speck at University of California Santa Barbara, and O. Briot at Université Montpellier II for the generous supply of InN samples. F. Reurings is acknowledged for his help with positron lifetime measurements. This work has been supported by the European Commission under the 7th Framework Program through the Marie Curie Initial Training Network RAINBOW, Contract No. PITN-Ga-2008-213238.

* Electronic address: christian.rauch@tkk.fi

- ¹ P. D. C. King, T. D. Veal, P. H. Jefferson, S. A. Hatfield, L. F. J. Piper, C. F. McConville, F. Fuchs, J. Furthmüller, F. Bechstedt, H. Lu, et al., Phys. Rev. B **77**, 045316 (2008).
- ² A. G. Bhuiyan, A. Hashimoto, and A. Yamamoto, J. Appl. Phys. **94**, 2779 (2003).
- ³ R. E. Jones, S. X. Li, E. E. Haller, H. C. M. van Genuchten, K. M. Yu, J. W. Ager, III, Z. Liliental-Weber, W. Walukiewicz, H. Lu, et al., Appl. Phys. Lett. **90**, 162103 (2007).
- ⁴ S. X. Li, K. M. Yu, J. Wu, R. E. Jones, W. Walukiewicz, J. W. Ager, W. Shan, E. E. Haller, H. Lu, and W. J. Schaff, Phys. Rev. B **71**, 161201 (2005).
- ⁵ L. F. J. Piper, T. D. Veal, C. F. McConville, H. Lu, and W. J. Schaff, Appl. Phys. Lett. **88**, 252109 (2006).
- ⁶ F. Tuomisto, A. Pelli, K. M. Yu, W. Walukiewicz, and W. J. Schaff, Phys. Rev. B **75**, 193201 (2007).
- ⁷ F. Reurings, C. Rauch, F. Tuomisto, R. E. Jones, K. M. Yu, W. Walukiewicz, and W. J. Schaff, Phys. Rev. B **82**, 153202 (2010).
- ⁸ C. Stampfl, C. G. Van de Walle, D. Vogel, P. Krüger, and J. Pollmann, Phys. Rev. B **61**, R7846 (2000).

- ⁹ X. M. Duan and C. Stampfl, Phys. Rev. B **77**, 115207 (2008).
- ¹⁰ X. M. Duan and C. Stampfl, Phys. Rev. B **79**, 035207 (2009).
- ¹¹ X. M. Duan and C. Stampfl, Phys. Rev. B **79**, 174202 (2009).
- ¹² C. G. Van de Walle, J. L. Lyons, and A. Janotti, Phys. Status Solidi A **207**, 1024 (2010).
- ¹³ I. Mahboob, T. D. Veal, C. F. McConville, H. Lu, and W. J. Schaff, Phys. Rev. Lett. **92**, 036804 (2004).
- ¹⁴ K. Saarinen, P. Hautojärvi, and C. Corbel, *Positron Annihilation Spectroscopy of Defects in Semiconductors*, vol. 51A of *Semiconductors and Semimetals* (Academic Press, New York, 1998).
- ¹⁵ J. Oila, A. Kemppinen, A. Laakso, K. Saarinen, W. Egger, L. Liskay, P. Sperr, H. Lu, and W. J. Schaff, Appl. Phys. Lett. **84**, 1486 (2004).
- ¹⁶ A. Laakso, J. Oila, A. Kemppinen, K. Saarinen, W. Egger, L. Liskay, P. Sperr, H. Lu, and W. J. Schaff, J. Cryst. Growth **269**, 41 (2004).
- ¹⁷ F. Reurings, F. Tuomisto, C. S. Gallinat, G. Koblmüller, and J. S. Speck, Appl. Phys. Lett. **97**, 251907 (2010).

- ¹⁸ A. Pelli, K. Saarinen, F. Tuomisto, S. Ruffenach, and O. Briot, *Appl. Phys. Lett.* **89**, 011911 (2006).
- ¹⁹ C. Rauch, F. Reurings, F. Tuomisto, T. D. Veal, C. F. McConville, H. Lu, W. J. Schaff, C. S. Gallinat, G. Koblmüller, J. S. Speck, et al., *Phys. Status Solidi A* **207**, 1083 (2010).
- ²⁰ H. Wang, D. S. Jiang, L. L. Wang, X. Sun, W. B. Liu, D. G. Zhao, J. J. Zhu, Z. S. Liu, Y. T. Wang, S. M. Zhang, et al., *J. Phys. D* **41**, 135403 (2008).
- ²¹ W. Walukiewicz, *Physica B* **302-303**, 123 (2001).
- ²² A. Uedono, S. F. Chichibu, M. Higashiwaki, T. Matsui, T. Ohdaira, and R. Suzuki, *J. Appl. Phys.* **97**, 043514 (2005).
- ²³ A. Uedono, S. Ishibashi, T. Ohdaira, and R. Suzuki, *J. Cryst. Growth* **311**, 3075 (2009).
- ²⁴ S. Hautakangas, I. Makkonen, V. Ranki, J. Puska, K. Saarinen, X. Xu, and D. C. Look, *Phys. Rev. B* **73**, 193301 (2006).
- ²⁵ I. Makkonen, M. Hakala, and M. J. Puska, *Phys. Rev. B* **73**, 035103 (2006).
- ²⁶ K. G. Lynn, J. R. MacDonald, R. A. Boie, L. C. Feldman, J. D. Gabbe, M. F. Robbins, E. Bonderup, and J. Golovchenko, *Phys. Rev. Lett.* **38**, 241 (1977).
- ²⁷ M. Alatalo, B. Barbiellini, M. Hakala, H. Kauppinen, T. Korhonen, M. J. Puska, K. Saarinen, P. Hautojärvi, and R. M. Nieminen, *Phys. Rev. B* **54**, 2397 (1996).
- ²⁸ E. Boroński and R. M. Nieminen, *Phys. Rev. B* **34**, 3820 (1986).
- ²⁹ P. E. Blöchl, *Phys. Rev. B* **50**, 17953 (1994).
- ³⁰ G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
- ³¹ C. Rauch, I. Makkonen, and F. Tuomisto, *Phys. Status Solidi C* (**in press**) (2011).
- ³² J. H. Edgar, ed., *Properties of Group-III Nitrides*, vol. EMIS Datareviews Series (IEE, London, 1994).
- ³³ M. J. Puska and R. M. Nieminen, *J. Phys. F* **13**, 333 (1983).
- ³⁴ F. Tuomisto, K. Saarinen, T. Paskova, B. Monemar, M. Bockowski, and T. Suski, *J. Appl. Phys.* **99**, 066105 (2006).
- ³⁵ J. Neugebauer and C. G. V. de Walle, *Appl. Phys. Lett.* **69**, 503 (1996).
- ³⁶ W. J. Schaff, H. Lu, L. F. Eastman, W. Walukiewicz, K. M. Yu, S. Keller, S. Kurtz, B. Keyes, and L. Gevillas, in *State-of-the-Art Program on Compound Semiconductors XLI and Nitride and Wide Bandgap Semiconductors for Sensors, Photonics, and Electronics V*, edited by H. M. Ng and A. G. Baca (Electrochemical Society, Honolulu, HI, 2004), vol. 2004-06 of *The Electrochemical Society Proceedings Series*, p. 358.
- ³⁷ B. Maleyre, O. Briot, and S. Ruffenach, *J. Cryst. Growth* **269**, 15 (2004).
- ³⁸ F. Reurings, F. Tuomisto, W. Egger, B. Loewe, L. Ravelli, S. Sojak, Z. Liliental-Weber, R. E. Jones, K. M. Yu, W. Walukiewicz, et al., *Phys. Status Solidi A* **207**, 1087 (2010).
- ³⁹ C. Rauch, I. Makkonen, F. Tuomisto, P. D. C. King, T. D. Veal, and C. F. McConville, unpublished (2011).